



A New Highly Thermally Stable Co(II)-coordination polymer with Semi-flexible Bis(Imidazole) Directed Secondary Building Unit: Solvothermal Synthesis and Structure

Fatih SEMERCI*  

Department of Energy Systems Engineering, Technology Faculty, Kırklareli University, Kırklareli, Turkey

Abstract: A new thermally highly stable 2D coordination polymer, formulated as $[\text{Co}(\mu_6\text{-abtc})_{0.5}(\mu\text{-obix})]_n$ (abtc = dioxygenated form of 3,3',5,5'-azobenzenetetracarboxylate) obtained employing the semi-flexible 1,2-bis(imidazole-1-ylmethyl)benzene (obix) linker in hydro(solvo)thermal method. The complex was characterized by various techniques such as IR spectroscopy, elemental analysis, single crystal and powder crystal analysis. Crystallographic study of complex **1** reveal that two metal(II) ions are linked by O atoms of carboxylate groups of abtc ligand to build paddle-wheel SBU (secondary building unit). These SBUs are stabilized by the connection of obix ligand. The Co(II) ions are μ_6 -bridged by hexadentate abtc ligand to generate 2D polymer layers with 3,4-connected binodal net (point symbol $\{4.6^2\}_2\{4^2.6^2.8^2\}$) and topological type is 3,4L13. Thermal analysis shows that complex **1** thermally stable up to 401 °C.

Keywords: Coordination polymers; bis(imidazole) ligands; 3,3',5,5'-azobenzenetetracarboxylate ligand; SBU.

Submitted: November 18, 2017. **Accepted:** July 15, 2018.

Cite this: Semerci F. A New Highly Thermally Stable Co(II)-coordination polymer with Semi-flexible Bis(Imidazole) Directed Secondary Building Unit: Solvothermal Synthesis and Structure. JOTCSA. 2018;5(2):1083-94.

DOI: <http://dx.doi.org/10.18596/jotcsa.355518>.

Corresponding author. E-mails: fsemerci@klu.edu.tr; f_semerci@hotmail.com.

INTRODUCTION

The quickly expanding area of coordination polymers has attracted interest for the fascinating architectures and their potential applications (1-5). Many efforts have been given for constructing new structures, new topologies, as well as new functionalities (6-8). These materials can be synthesized relying on the mixture of metal salts, carboxylate-based ligand and N-donor bridging ligands (9-12). The coordination polymers can be synthesis by using highly symmetrical multifunctional organic ligands owing to their various coordination behavior and special topologies. Furthermore, secondary building units (SBUs) that can predict the structures of

coordination polymers are largely utilized to construct them (13-15).

Properties of flexible coordination polymers can be synthesis practically at will by a preference of flexible ligands (16). The employment of flexible ligands often gives rise to increased disorder, which hampers the arrangement of self-assembly of coordination polymers. Nonetheless, flexible ligands can appropriate the coordinative demands of metal ions and form architecture in another way unavailable with rigid ligands (17).

Azobenzenecarboxylic acid compounds such as azobenzenedicarboxylic (18), azobenzene-tricarboxylic, (19) and

azobenzenetetracarboxylic acids (20-30) were employed to synthesis functional materials. The rigid 3,3',5,5'-azobenzenetetracarboxylate (abtc^{4-}) ligand has four carboxylate functional group, and they can be deprotonated and can be oxidized to generate an azoxy structure in the reaction media to build various architectures. In these architectures, highly strong metal-oxygen bonds can improve stability of the framework. Additionally, an important and useful strategy for synthesis coordination polymers with interesting structures is to employ semi-flexible imidazole-based ligands (31-33). The semi-flexible N-donor ligand, obix is a wise choice for the synthesis of coordination polymers (11, 34).

Taking all these into account, abtcH_4 and semi-flexible bis(imidazole) derivative ligands, namely obix, were prepared and their Co(II) coordination polymer, $[\text{Co}(\mu_6\text{-abtc})_{0.5}(\mu\text{-obix})]_n$ was synthesized. The synthesized complex was structurally characterized by various techniques such as elemental analysis, IR spectroscopy, and X-ray diffraction. Moreover, thermal and topological analysis were studied.

MATERIAL AND METHODS

All starting materials were commercially available and AR grade. Obix and abtcH_4 ligands were synthesized according to previous studies (34, 35). PerkinElmer 2400C Elemental Analyzer was used to elemental analyses (C, H and N). The IR spectrum was taken in the range of $4000\text{--}400\text{ cm}^{-1}$ with a Bruker Tensor 27 spectrometer. TG, DTG and DTA curves are recorded in the static air atmosphere in the range of $30\text{--}700\text{ }^\circ\text{C}$ with platinum crucibles.

Suitable crystals of **1** were selected for data collections, which were performed on a Bruker

D8-QUEST diffractometer equipped with graphite-monochromatic Mo-K α radiation. The structure of complex **1** was obtained by direct methods using OLEX2 (36) and SHELXS-97 (37) software. All non-hydrogen atoms were refined anisotropically by full-matrix least squares methods in SHELXL-97 (37). The figures were drawn by using MERCURY (38). Topological analysis was performed using ToposPro software (39).

Synthesis of $[\text{Co}(\mu_6\text{-abtc})_{0.5}(\mu\text{-obix})]_n$

(1): A mixture of abtcH_4 (0.25 g, 0.69 mmol), obix (0.16 g; 0.69 mmol), $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (0.40 g; 1.38 mmol), DMF (10 mL) and two drops of conc. HNO_3 was mixed at $30\text{ }^\circ\text{C}$ for half an hour. The obtained solution was sealed in a glass vial and heated at $120\text{ }^\circ\text{C}$ for 3 days. Red-colored crystals of **1** were obtained (yield: 0.16 g, 12.17% based on $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$). Anal. Calcd. for $\text{C}_{22}\text{H}_{19}\text{N}_5\text{O}_4\text{Co}$: C, 55.47; H, 4.02; N, 14.70; Found: C, 56.03; H, 4.38; N, 13.84. IR data (KBr, cm^{-1}): 3142w, 3122w, 2955w, 2854w, 1622s, 1573sh, 1527sh, 1443m, 1408m, 1368s, 1233w, 1111w, 1090w, 937w, 829w, 780m, 707s, 654m, 615w, 566w, 490w, 471sh.

RESULTS AND DISCUSSION

Synthesis and Spectral Characterization:

Obix and abtcH_4 ligands were synthesized, and its Co(II)-complex was obtained in acidic medium in DMF. Elemental analysis results agreed with single crystal X-ray results. FT-IR spectra of complex **1** is given in **Figure 1**. In the FT-IR spectrum of **1**, the bands observed between 3142 and 2854 cm^{-1} are assigned to aromatic and aliphatic $\nu(\text{C-H})$ stretching vibrations, respectively. The stretching vibrations of carboxylate groups of abtc^{4-} ligand are seen at 1622 and 1443 cm^{-1} , respectively.

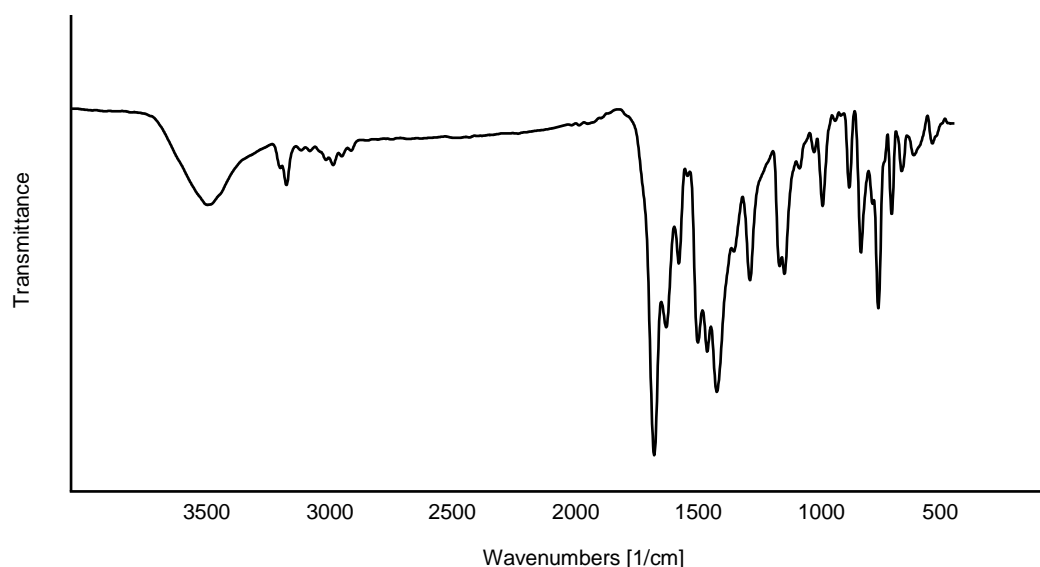


Figure 1. FT-IR spectrum of **1**.

Crystal Structure Description of $[\text{Co}(\mu_6\text{-abtc})_{0.5}(\mu\text{-obix})]_n$ (1**):** The X-ray crystal structural analysis shows that complex **1** is a two-dimensional (2D) coordination polymer. Complex **1** has monoclinic system and it has space group of $P2_1/n$. The asymmetric unit of **1** includes Co(II) ion, half abtc anionic ligand and one obix ligand (**Figure 2**). Each Co(II) ion in **1** shows a distorted trigonal bipyramidal environment composed of three carboxylic O atoms from different abtc⁴⁻ anions [Co1–O1 = 1.980 (3); Co1–O2ⁱ = 2.009 (3) and Co1–O3ⁱⁱ = 1.958 (3) Å ((i) $-x+1, -y+1, -z$; (ii) $x+1, y, z$)] and two nitrogen atoms from two different obix ligands [Co1–N1 = 2.106 (3) and Co1–N4ⁱ = 2.101 (3) Å]. Secondary building units (SBU) in complex **1** were formed

by two Co(II) ions that are bridged by carboxylate groups of abtc ligands. In SBU units obix ligands exhibit chair-conformation and these SBUs are stabilized by the coordination of obix ligand (34). The Co...Co distance in SBU is 3.917 (4) Å. The SBU units are bridged by oxygen atoms of anionic ligands to generate 1D structures of **1** (Figure 3). Adjacent 1D structures are bridged by other carboxylate atoms of abtc ligands to achieve layered 2D unit (Figure 4). The neighboring 2D units are further connected via van der Waals interaction, thus generating the 3D supramolecular structure (Figure 5). Topologically, complex **1** is 3,4-connected binodal net with point symbol $\{4.6^2\}_2\{4^2.6^2.8^2\}$ (Figure 6).

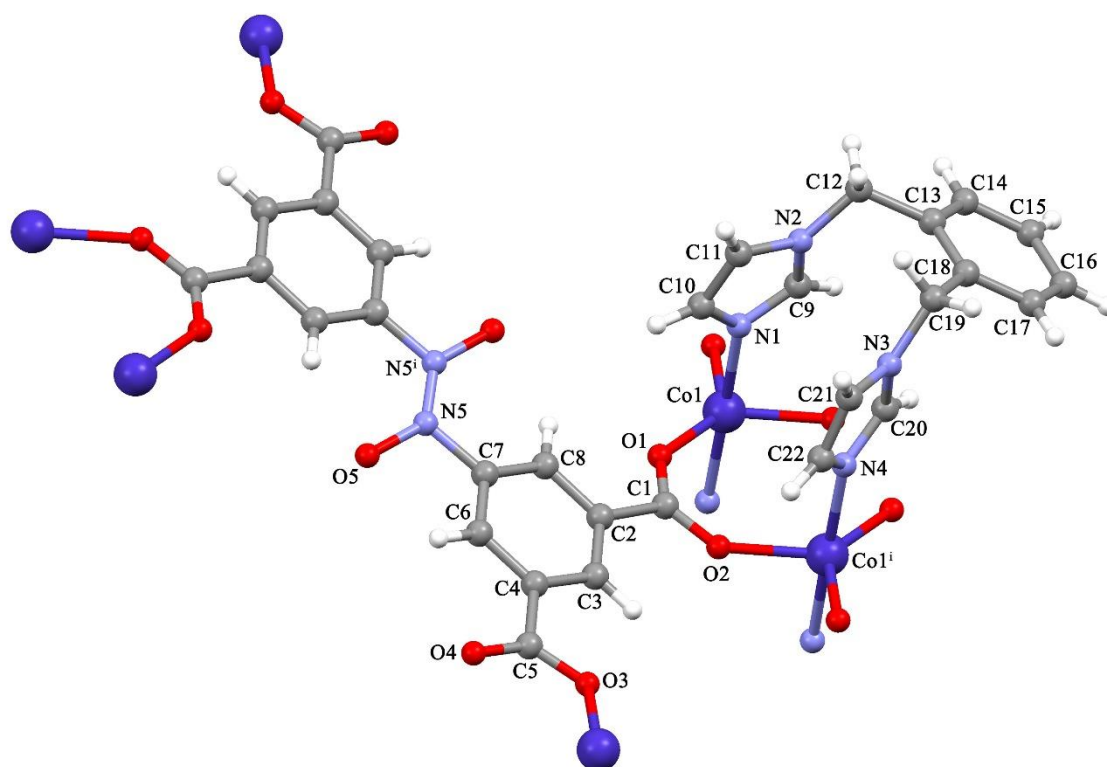


Figure 2. The molecular structure of **1**.

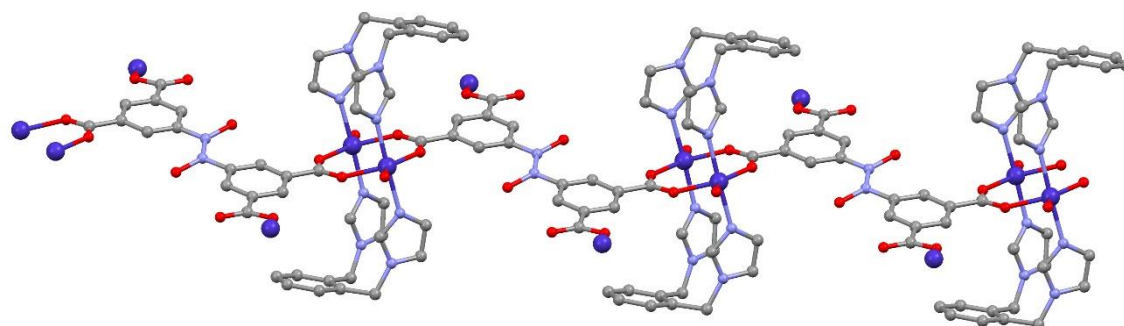


Figure 3. 1D structure of complex **1**.

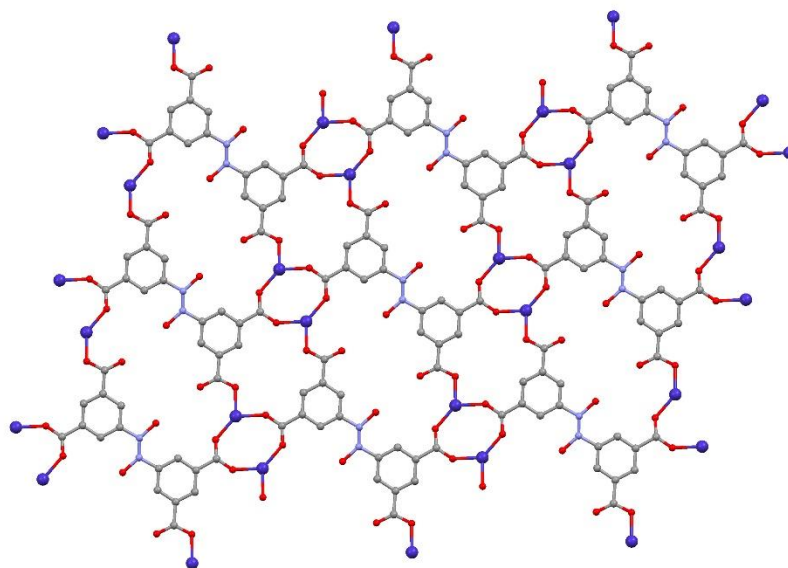


Figure 4. 2D structure of complex **1**.

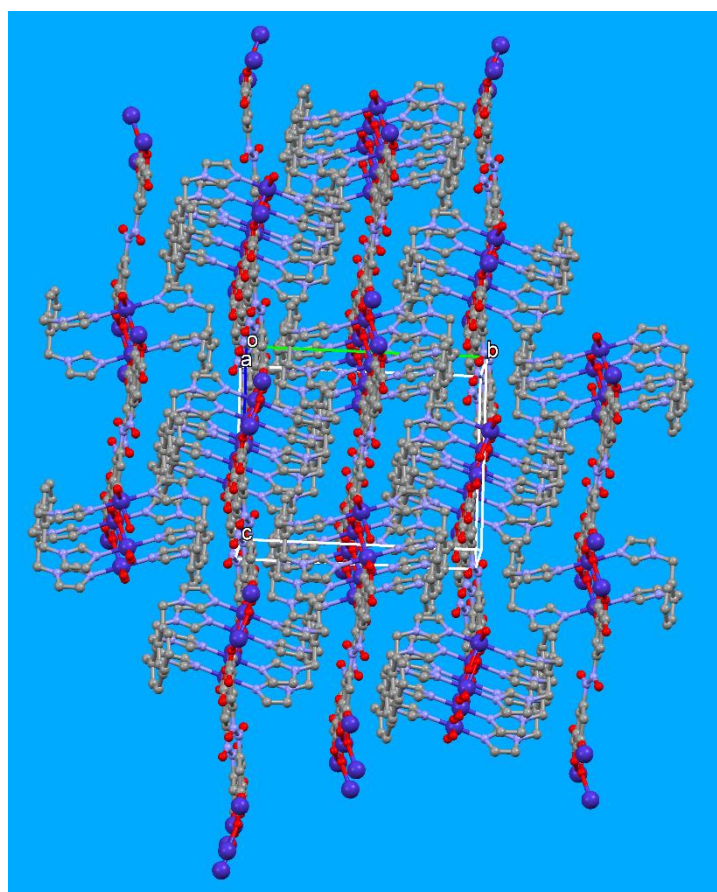


Figure 5. 3D structure of complex **1** with unit cell.

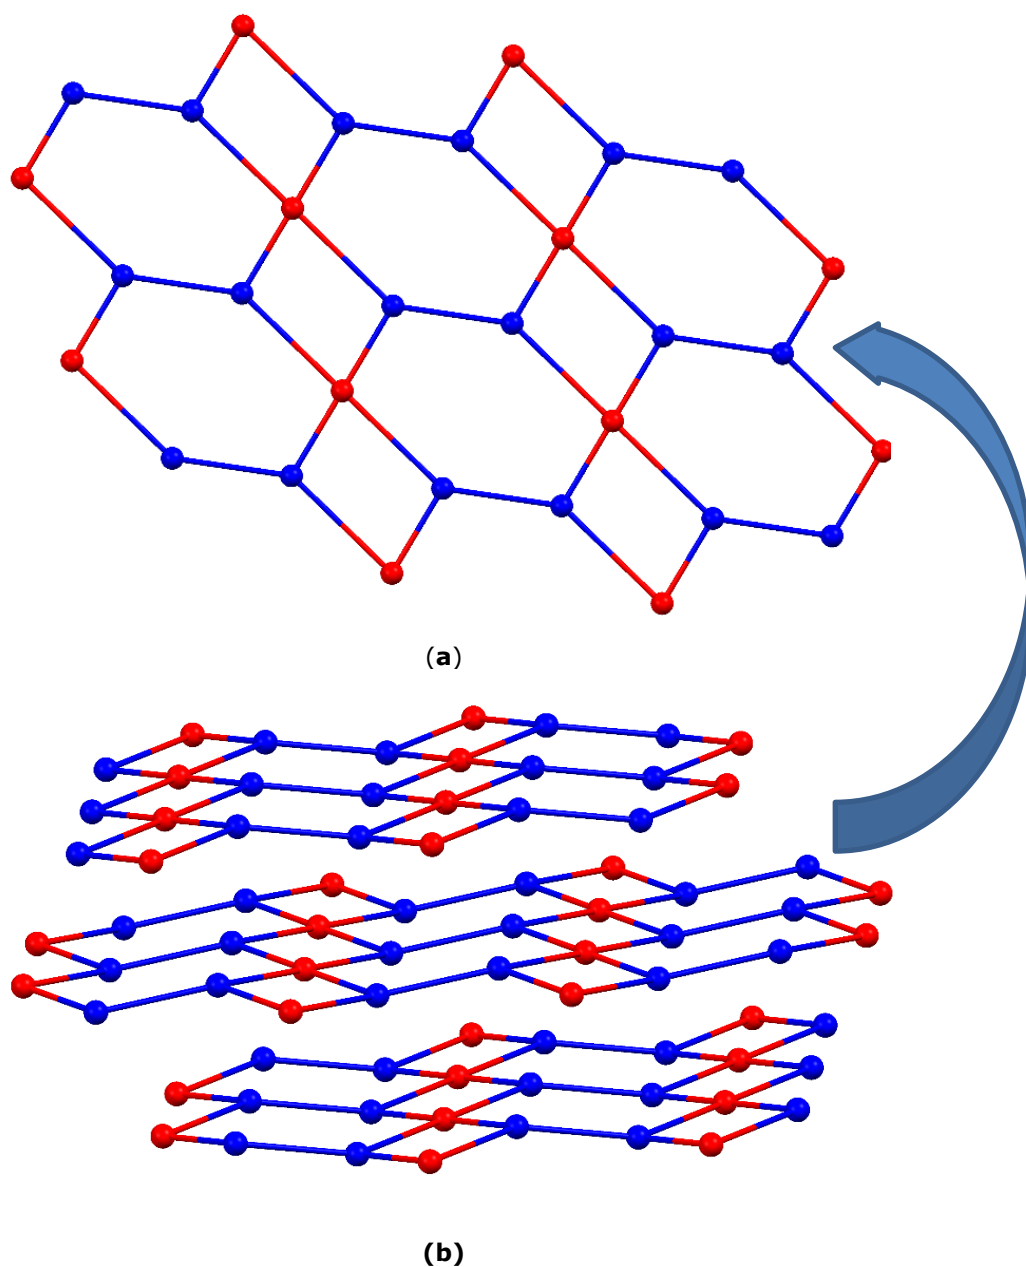


Figure 6. Topological presentation of complex 1.

Table 1. Crystal data and structure refinement parameters for complex **1**.

Item	Value
Crystal data	1
Empirical formula	C ₂₂ H ₁₇ CoN ₅ O ₅
Formula weight	490.34
Crystal system	Monoclinic
Space group	<i>P</i> 2 ₁ / <i>n</i>
<i>a</i> (Å)	9.9166 (2)
<i>b</i> (Å)	15.6800 (4)
<i>c</i> (Å)	14.0749 (3)
α (°)	90
β (°)	109.3028(11)
γ (°)	90
<i>V</i> (Å ³)	2065.51 (8)
<i>Z</i>	4
<i>D</i> _c (g cm ⁻³)	1.577
μ (mm ⁻¹)	0.88
θ range (°)	2.5–27.5
Measured refls.	34803
Independent refls.	4727
<i>R</i> _{int}	0.034
<i>S</i>	1.06
<i>R</i> ₁ / <i>wR</i> ₂	0.056/0.159
$\Delta\rho_{\max}/\Delta\rho_{\min}$ (eÅ ⁻³)	2.05 / -1.24

Table 2. Selected bond distances (Å) and angles (°) for **1**.


Bond Lengths (Å)			
Co1—O1	1.980 (3)	Co1—N1	2.106 (3)
Co1—O2 ⁱ	2.009 (3)	Co1—N4 ⁱ	2.101 (3)
Co1—O3 ⁱⁱ	1.958 (3)		
Angles (°)			
N4 ⁱ —Co1—N1	176.37(11)	O2 ⁱ —Co1—N4 ⁱ	91.87 (11)
O3 ⁱⁱ —Co1—O1	136.8 (3)	O2 ⁱ —Co1—N1	89.45 (11)
O3 ⁱⁱ —Co1—N1	93.24 (14)	O1—Co1—N4 ⁱ	89.75 (11)
O3 ⁱⁱ —Co1—O2 ⁱ	93.9 (3)	O1—Co1—O2 ⁱ	129.26 (18)
O3 ⁱⁱ —Co1—N4 ⁱ	90.05 (15)	O1—Co1—N1	86.79 (11)

Symmetry codes: (i) $-x+1, -y+1, -z$; (ii) $x+1, y, z$; (iii) $-x+1, -y+1, -z+1$; (iv) $x-1, y, z$.

Thermal Analysis and X-ray Powder Diffraction: The thermal behaviors and thermal stability of complex **1** were investigated by TG/DTA techniques in a dry air atmosphere with a heating rate of 10 °C/min in the temperature range 30-700 °C (Figure 7(a)). Complex **1** is thermally stable up to 401 °C, respectively. For complex **1**, on further heating, the complex is exothermically decomposed. The final residual product of

complex **1** is possible CoO (obsd.: 15.21%, calcd.: 15.73%).

The crystalline product of **1** was characterized by powder X-ray diffraction (PXRD) (Figure 7(b)). The experimental XRD pattern is comparable with the results simulated from the single crystal data. This is show that the purity of the synthesized samples.

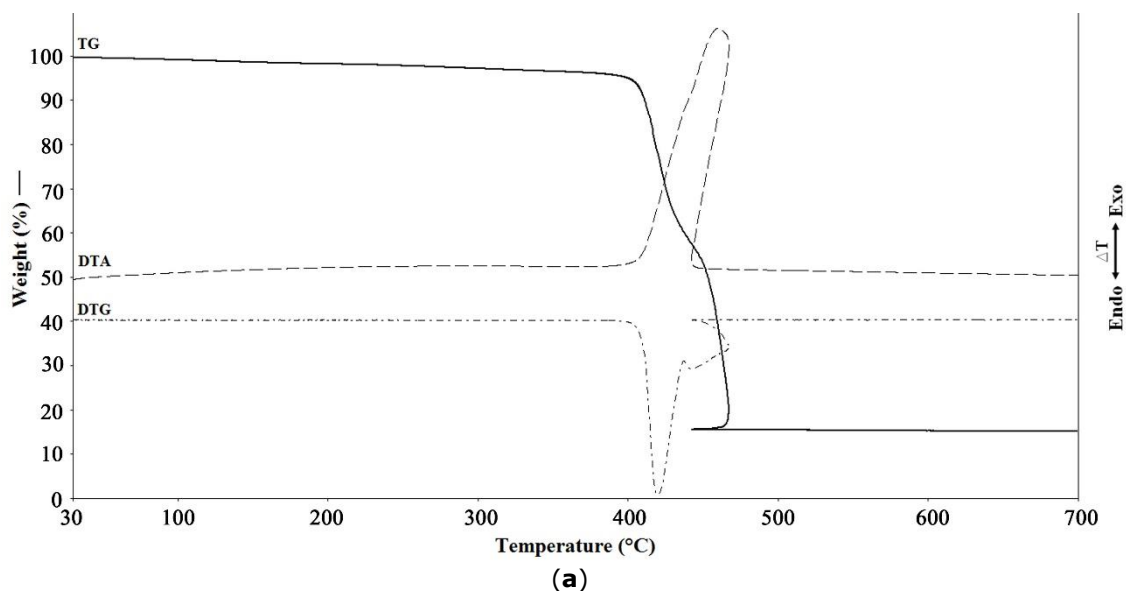

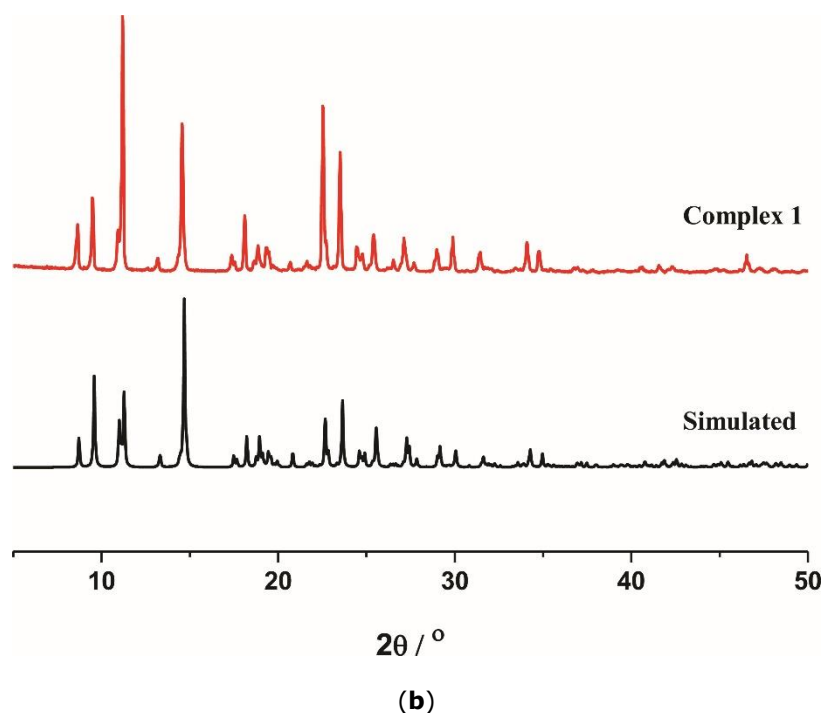


Figure 7. (a) Thermal analysis (TG, DTG and DTA) curves (b) XRPD pattern of complex **1**.

CONCLUSION

A new 2D Co(II)-coordination polymer with 3,3',5,5'-azobenzenetetracarboxylate and semi-flexible obix was synthesized and structurally characterized. μ_6 -bridged by hexadentate abtc ligands are coordinated by Co(II) ions to generate 2D polymer chains with 3,4-connected binodal net (point symbol $\{4.6^2\}_2\{4^2.6^2.8^2\}$) and topological type is 3,4L13.

REFERENCES

1. Lu JY. Crystal engineering of Cu-containing metal-organic coordination polymers under hydrothermal conditions. *Coordination Chemistry Reviews*. 2003;246(1):327-47.
2. Janiak C. Engineering coordination polymers towards applications. *Dalton Transactions*. 2003(14):2781-804.
3. Thapa KB, Chen J-D. Crystal engineering of coordination polymers containing flexible bis-pyridyl-bis-amide ligands. *CrystEngComm*. 2015;17(25):4611-26.
4. Biradha K, Sarkar M, Rajput L. Crystal engineering of coordination polymers using 4,4[prime or minute]-bipyridine as a bond between transition metal atoms. *Chemical Communications*. 2006(40):4169-79.
5. Semerci F, Yesilel OZ, Keskin S, Darcan C, Tas M, Dal H. Construction of homo- and heterometallic-pyridine-2,3-dicarboxylate metallosupramolecular networks with structural diversity: 1D T5(2) water tape and unexpected coordination mode of pyridine-2,3-dicarboxylate. *CrystEngComm*. 2013;15(6):1244-56.
6. Li X-L, Liu G-Z, Xin L-Y, Wang L-Y. Binuclear and tetranuclear Mn(II) clusters in coordination polymers derived from semirigid tetracarboxylate and N-donor ligands: syntheses, new topology structures and magnetism. *Journal of Solid State Chemistry*. 2017;246:252-7.
7. Ma J, Tran LD, Matzger AJ. Toward Topology Prediction in Zr-Based Microporous Coordination Polymers: The Role of Linker Geometry and Flexibility. *Crystal Growth & Design*. 2016;16(7):4148-53.
8. Zhu X-D, Li Y, Gao J-G, Wang F-H, Li Q-H, Yang H-X, et al. Two new coordination polymers with flexible alicyclic carboxylate and bipyridyl co-ligands bearing trinuclear $[\text{Ni}_3(\text{COO})_6]$ SBUs: Synthesis, crystal structures, and magnetic properties. *Journal of Molecular Structure*. 2017;1130:89-95.
9. Semerci F. Syntheses and photoluminescence properties of new Zn (II) and Cd (II) coordination polymers prepared from 5-sulfoisophthalate ligand. *Turkish Journal of Chemistry*. 2017;41(2):243-55.

10. Yang Y, Yang J, Du P, Liu Y-Y, Ma J-F. A series of metal-organic frameworks based on a semi-rigid bifunctional ligand 5-[(1H-1,2,4-triazol-1-yl)methoxy] isophthalic acid and flexible N-donor bridging ligands. *CrystEngComm*. 2014;16(28):6380-90.
11. Semerci F, Yeşilel OZ, Yüksel F. Self-assembly of three new metal organic coordination networks based on 1,2-bis(imidazol-1-yl-methyl)benzene. *Polyhedron*. 2015;102:1-7.
12. Semerci F, Yeşilel OZ, Yüksel F, Şahin O. One-pot synthesis of two new metal-organic networks: hydrogen bonded mononuclear Cu(II) complex and mixed-valence Cu(I,II) coordination polymer with encapsulated 14-membered unique water cluster. *Inorganic Chemistry Communications*. 2015;62:29-33.
13. Schoedel A, Li M, Li D, O'Keeffe M, Yaghi OM. Structures of Metal-Organic Frameworks with Rod Secondary Building Units. *Chemical Reviews*. 2016;116(19):12466-535.
14. Ren G-J, Chang Z, Xu J, Hu Z, Liu Y-Q, Xu Y-L, et al. Construction of a polyhedron decorated MOF with a unique network through the combination of two classic secondary building units. *Chemical Communications*. 2016;52(10):2079-82.
15. Eddaoudi M, Moler DB, Li H, Chen B, Reineke TM, O'Keeffe M, et al. Modular Chemistry: Secondary Building Units as a Basis for the Design of Highly Porous and Robust Metal-Organic Carboxylate Frameworks. *Accounts of Chemical Research*. 2001;34(4):319-30.
16. Liu T-F, Lu J, Cao R. Coordination polymers based on flexible ditopic carboxylate or nitrogen-donor ligands. *CrystEngComm*. 2010;12(3):660-70.
17. Heim D, Écija D, Seufert K, Auwärter W, Auricchio C, Fabbro C, et al. Self-Assembly of Flexible One-Dimensional Coordination Polymers on Metal Surfaces. *Journal of the American Chemical Society*. 2010;132(19):6783-90.
18. Reineke TM, Eddaoudi M, Moler D, O'Keeffe M, Yaghi OM. Large Free Volume in Maximally Interpenetrating Networks: The Role of Secondary Building Units Exemplified by $\text{Tb}_2(\text{ADB})_3[(\text{CH}_3)_2\text{SO}]_4 \cdot 16[(\text{CH}_3)_2\text{SO}]_1$. *Journal of the American Chemical Society*. 2000;122(19):4843-4.
19. Meng M, Zhong D-C, Lu T-B. Three porous metal-organic frameworks based on an azobenzenetricarboxylate ligand: synthesis, structures, and magnetic properties. *CrystEngComm*. 2011;13(22):6794-800.
20. Lee Y-G, Moon HR, Cheon YE, Suh MP. A Comparison of the H₂ Sorption Capacities of Isostructural Metal-Organic Frameworks With and Without Accessible Metal Sites: $[\{\text{Zn}_2(\text{abtc})(\text{dmf})_2\}_3]$ and $[\{\text{Cu}_2(\text{abtc})(\text{dmf})_2\}_3]$ versus $[\{\text{Cu}_2(\text{abtc})\}_3]$. *Angewandte Chemie International Edition*. 2008;47(40):7741-5.
21. Zhang S, Ma J, Zhang X, Duan E, Cheng P. Assembly of Metal-Organic Frameworks Based on 3,3',5,5'-Azobenzene-tetracarboxylic Acid: Photoluminescences, Magnetic Properties, and Gas Separations. *Inorganic Chemistry*. 2015;54(2):586-95.
22. Xu Y-C, Chen Y, Qiu H-J, Zeng X-S, Xu H-L, Li J, et al. Metal nuclearity affects network connectivity: a series of highly connected metal-organic frameworks based on polynuclear metal clusters as secondary building units. *CrystEngComm*. 2016;18(42):8182-93.
23. Li Y-P, Zhang L-J, Ji W-J. Synthesis, characterization, crystal structure of magnesium compound based 3, 3', 5, 5'-azobenzentetracarboxylic acid and application as high-performance heterogeneous catalyst for cyanosilylation. *Journal of Molecular Structure*. 2017;1133:607-14.
24. Fan L, Fan W, Li B, Liu X, Zhao X, Zhang X. Structural diversities and related properties of four coordination polymers synthesized from original ligand of 3,3[prime or minute],5,5[prime or minute]-azobenzene-tetracarboxylic acid. *Dalton Transactions*. 2015;44(5):2380-9.
25. Liu W, Ye L, Liu X, Yuan L, Jiang J, Yan C. Hydrothermal syntheses, structures and luminescent properties of d10 metal-organic frameworks based on rigid 3,3[prime or minute],5,5[prime or minute]-azobenzene-tetracarboxylic acid. *CrystEngComm*. 2008;10(10):1395-403.
26. Miller SR, Alvarez E, Fradcourt L, Devic T, Wuttke S, Wheatley PS, et al. A rare example of a porous Ca-MOF for the controlled release of biologically active NO. *Chemical Communications*. 2013;49(71):7773-5.

27. Arıcı M, Yeşilel OZ, Taş M. Coordination Polymers Assembled From 3,3',5,5'-Azobenzenetetracarboxylic Acid and Different Bis(imidazole) Ligands with Varying Flexibility. *Crystal Growth & Design*. 2015;15(6):3024-31.
28. Arıcı M, Yeşilel OZ, Taş M, Demiral H. Effect of Solvent Molecule in Pore for Flexible Porous Coordination Polymer upon Gas Adsorption and Iodine Encapsulation. *Inorganic Chemistry*. 2015;54(23):11283-91.
29. Arıcı M, Yeşilel OZ, Taş M, Demiral H, Erer H. Construction, Structural Diversity, and Properties of Seven Zn(II)-Coordination Polymers Based on 3,3',5,5'-Azobenzenetetracarboxylic Acid and Flexible Substitute Bis(imidazole) Linkers. *Crystal Growth & Design*. 2016;16(9):5448-59.
30. Arıcı M, Yeşilel OZ, Taş M. Cd(II)-coordination polymers based on tetracarboxylic acid and diverse bis(imidazole) ligands: Synthesis, structural diversity and photoluminescence properties. *Journal of Solid State Chemistry*. 2017;245:146-51.
31. Erer H, Yeşilel OZ, Arıcı M. A Series of Zinc(II) 3D → 3D Interpenetrated Coordination Polymers Based On Thiophene-2,5-dicarboxylate and Bis(Imidazole) Derivative Linkers. *Crystal Growth & Design*. 2015;15(7):3201-11.
32. Erer H, Karaçam S, Arıcı M, Yeşilel OZ, Çelik Ö. Hydrothermal synthesis and characterization of Zn(II), Cd(II) and Ag(I)-saccharinate complexes containing bis(imidazol) derivatives. *Polyhedron*. 2015;98:180-9.
33. Wang XX, Liu YG, Van Hecke K, Goltsev A, Cui GH. Three Silver(I) Coordination Polymers Constructed from Flexible Bis(benzimidazole) and Carboxylates Ligands. *Zeitschrift für anorganische und allgemeine Chemie*. 2015;641(5):903-10.
34. Tan H-Y, Zhang H-X, Ou H-D, Kang B-S. Chair-form [Ag₂(1,2-bimb)₂]²⁺ in silver(I) complexes containing the ditopic ligand 1,2-bis(1-imidazolylmethyl)benzene (1,2-bimb). *Inorganica Chimica Acta*. 2004;357(3):869-74.
35. Wang X-S, Ma S, Rauch K, Simmons JM, Yuan D, Wang X, et al. Metal–Organic Frameworks Based on Double-Bond-Coupled Di-Isophthalate Linkers with High Hydrogen and Methane Uptakes. *Chemistry of Materials*. 2008;20(9):3145-52.
36. Dolomanov OV, Bourhis LJ, Gildea RJ, Howard JAK, Puschmann H. OLEX2: a complete structure solution, refinement and analysis program. *Journal of Applied Crystallography*. 2009;42(2):339-41.
37. Sheldrick G. A short history of SHELX. *Acta Crystallogr A*. 2008;64(1):112-22.
38. Macrae CF, Edgington PR, McCabe P, Pidcock E, Shields GP, Taylor R, et al. Mercury: visualization and analysis of crystal structures. *Journal of Applied Crystallography*. 2006;39(3):453-7.
39. Blatov VA, Shevchenko AP, Proserpio DM. Applied Topological Analysis of Crystal Structures with the Program Package ToposPro. *Cryst Growth Des*. 2014;14(7):3576-86.

